

# **SF-71**

FLUX CORED ARC WELDING CONSUMABLE  
FOR WELDING OF MILD & 490MPa CLASS  
HIGH TENSILE STEEL

2022.02

**❖ Specification**

<b><i>AWS A5.20</i></b>	E71T-1C
<b><i>(AWS A5.20M)</i></b>	E491T-1C)
<b><i>EN ISO 17632-A</i></b>	T42 0 P C1 1
<b><i>JIS Z3313</i></b>	T49J 0 T1-1 C A-U
<b><i>KS D 7104</i></b>	YFW-C50DR

**❖ Applications**

All position welding of ship buildings, machinery, bridges, building, vehicles using mild and higher strength steels.

**❖ Characteristics on Usage**

SF-71 is a titania type flux cored wire for all position welding with CO<sub>2</sub>. Compared with solid wire, spatter loss is low, bead appearance is a beautiful and arc is soft with good stability. Slag covering is uniform with good removal.

**❖ Note on Usage**

1. For preheating guidelines, please refer to your local standards and codes relative to your best practices.
2. One-side welding defects such as hot cracking may occur with wrong welding parameter such as high welding speed.
3. Use 100% CO<sub>2</sub> gas.






## Mechanical Properties & Chemical Composition of All Weld Metal

### ❖ Welding Conditions

Method by AWS Spec.

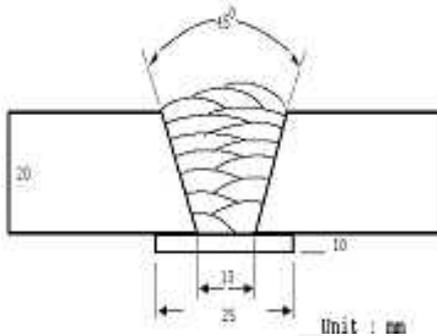

[ Joint Preparation & Layer Details ]

<b>Welding Position</b>	: 1G(PA)
<b>Diameter</b>	: 1.4mm (0.052in)
<b>Shielding Gas</b>	: 100%CO <sub>2</sub>
<b>Flow Rate</b>	: 20 ℓ /min
<b>Amp./ Volt.</b>	: 300A / 32V
<b>Stick-Out</b>	: 20~25mm (0.79~0.98in)
<b>Pre-Heat</b>	: R.T .
<b>Interpass Temp.</b>	: 150±15℃ (302±59°F)
<b>Polarity</b>	: DC(+)

### ❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)	
	YS MPa (lbs/in <sup>2</sup> )	TS MPa (lbs/in <sup>2</sup> )	EL (%)	-1℃ (30°F)	-18℃ (0°F)
SF-71	538 (78,000)	575 (83,000)	27.5	87 (64)	52 (38)
AWS A5.20 E71T-1C	≥ 390 (56,000)	490~670 (70,000~ 97,000)	≥ 22	≥ 27J at -18℃ (≥ 20ft · lbs at 0°F)	

### ❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S
SF-71	0.041	0.52	1.29	0.010	0.008
AWS A5.20 E71T-1C	≤ 0.12	≤ 0.9	≤ 1.75	≤ 0.03	≤ 0.03


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



## Mechanical Properties & Chemical Composition of All Weld Metal

### ❖ Welding Conditions

Method by AWS Spec.

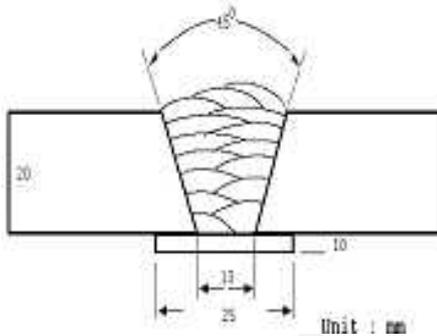

[ Joint Preparation & Layer Details ]

<b>Welding Position</b>	: 1G(PA)
<b>Diameter</b>	: 1.6mm (1/16in)
<b>Shielding Gas</b>	: 100%CO <sub>2</sub>
<b>Flow Rate</b>	: 20 ℓ /min
<b>Amp./ Volt.</b>	: 320~330A / 29~30V
<b>Stick-Out</b>	: 20~25mm (0.79~0.98in)
<b>Pre-Heat</b>	: R.T .
<b>Interpass Temp.</b>	: 150±15℃ (302±59°F)
<b>Polarity</b>	: DC(+)

### ❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)	
	YS MPa (lbs/in <sup>2</sup> )	TS MPa (lbs/in <sup>2</sup> )	EL (%)	-1℃ (30°F)	-18℃ (0°F)
SF-71	540 (78,000)	580 (84,000)	27.5	85 (63)	56 (41)
AWS A5.20 E71T-1C	≥ 390 (56,000)	490~670 (70,000~ 97,000)	≥ 22	≥ 27J at -18℃ (≥ 20ft · lbs at 0°F)	

### ❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S
SF-71	0.04	0.50	1.30	0.011	0.009
AWS A5.20 E71T-1C	≤ 0.12	≤ 0.9	≤ 1.75	≤ 0.03	≤ 0.03

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



## Welding Efficiency

### ❖ Deposition Rate & Efficiency

Consumable (size)	Welding Conditions		Wire Feed Speed m/min (in/min)	Deposition Efficiency %	Deposition Rate kg/hr(lb/hr)
	Amp.(A)	Volt.(V)			
<b>SF- 71</b>  <b>1.2mm</b> <b>(0.045in)</b>	200	26	10.2 (400)	84~87	3.4 (7.5)
	250	28	11.5 (450)	85~88	4.5 (9.9)
	300	33	15.3 (600)	86~88	5.2 (11.4)
<b>SF- 71</b>  <b>1.4mm</b> <b>(0.052in)</b>	250	28	7.6 (300)	85~87	3.9 (8.6)
	300	32	10.2 (400)	85~88	4.8 (10.6)
	330	36	12.8 (500)	86~89	5.8 (12.8)
<b>SF- 71</b>  <b>1.6mm</b> <b>(1/16in)</b>	280	31	6.4 (250)	85~88	4.2 (9.2)
	330	33	7.6 (300)	86~88	4.8 (10.6)
	350	34	8.1 (320)	87~89	5.3 (11.7)
	400	38	9.2 (360)	87~90	5.7 (12.5)
<b>Remark</b>				Deposition efficiency =(Deposited metal weight/ Wire weight used)×100	Deposition rate =(Deposited metal weight/ Welding time,min.)×60

\* Shielding Gas : 100%CO<sub>2</sub>

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



## Diffusible Hydrogen Content

### ❖ Welding Conditions

<b>Diameter</b>	: 1.4mm (0.052in)	<b>Amps(A) / Volts(V)</b>	: 240A / 27V
<b>Shielding Gas</b>	: 100%CO <sub>2</sub>	<b>Stick-Out</b>	: 20~25mm (0.79~0.98in)
<b>Flow Rate</b>	: 20 l /min	<b>Welding Speed</b>	: 30 cm/min (12 in/min)
<b>Welding Position</b>	: 1G (PA)	<b>Current Type &amp; Polarity</b>	: DC(+)

### ❖ Hydrogen Analysis Using Gas Chromatography Method

<b>Hydrogen Evolution Time</b>	: 72 hrs
<b>Evolution Temp.</b>	: 45 °C (113°F)
<b>Barometric Pressure</b>	: 780 mm-Hg

### ❖ Result(ml/100g Weld Metal)

X1	X2	X3	X4
<b>6.0</b>	<b>6.4</b>	<b>5.9</b>	<b>6.2</b>

**Average Hydrogen Content 6.1 ml / 100g Weld Metal**



## Proper Welding Condition

### ❖ Proper Current Range

Consumable	Shielding Gas	Welding Position	Wire Dia.		
			1.2mm (0.045in)	1.4mm (0.052in)	1.6mm (1/16in)
SF-71	100%CO <sub>2</sub>	F & HF	120~300Amp	150~350Amp	150~360Amp
		V-Up & OH	120~260Amp	180~280Amp	180~280mp
		V-Down	200~300Amp	220~320Amp	250~320Amp

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



## Approvals

### ❖ AUTHORIZED APPROVAL DETAILS

Welding Position	Register of shipping & Size					
	KR	ABS	LR	BV	DNV	NK
All V-Down	2SMG, 2YSMG ©H10  1.2~1.6mm (0.045~1/16in)	2SAH10, 2YSA  1.2~1.6mm (0.045~1/16in)	2S, 2YSH10  1.2~1.6mm (0.045~1/16in)	SA2M,2YMHH A2,2YMHH  1.2~1.6mm (0.045~1/16in)	IYMSH15  1.2~1.6mm (0.045~1/16in)	KSW52Y40G ©H10  1.2~1.6mm (0.045~1/16in)

### ❖ F No & A No

F No	A No
6	1