

SF-71MC

FLUX CORED ARC WELDING CONSUMABLE
FOR WELDING OF MILD & 490MPa CLASS
HIGH TENSILE STEEL

2022.02

HYUNDAI WELDING CO., LTD.



❖ Specification

AWS A5.20 E71T-1C,-1M,-9C,-9M,-12C,-12M

AWS A5.20M E491T-1C,-1M,-9C,-9M,-12C,-12M

EN ISO 17632-A T46 2 P C1 1 H10, T46 3 P M21 1 H10

AWS D1.8

Wire Dia. mm(in)		
1.2(0.045)	1.4(0.052)	1.6(1/16)

* AWS D1.8 is available upon request

❖ Applications

All position welding of ship hulls, vehicles, bridges, chemical plant machinery and other metal fabrication

❖ Characteristics on Usage

SF-71MC is a titania flux cored wire applicable for all-position welding by 100% CO₂ shielding gas or Ar – 20~25% CO₂ shielding gas.

Less spattering and good slag detachability shorten the time of bead grinding operation.

❖ Note on Usage


1. For preheating guidelines, please refer to your local standards and codes relative to your best practices.
2. Use 100% CO₂ or Ar – 20~25% CO₂ shielding gas



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

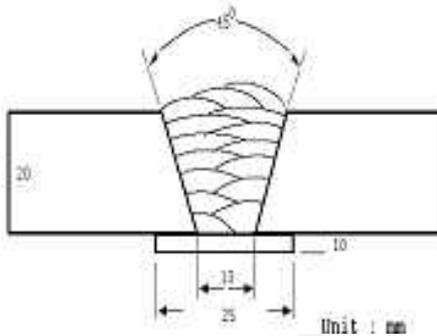

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.2mm (0.045in)
Shielding Gas	: 100% CO ₂ Ar-20%CO ₂
Flow Rate	: 20 ℓ /min
Amp./ Volt.	: 280A / 32V (100% CO ₂) 280A / 30V (Ar-20%CO ₂)
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T (°C, °F)
Interpass Temp	: 150±15°C (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Shielding gas	Tensile Test			CVN Impact Test J(ft · lbs)	
		YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18°C (0°F)	-29°C (-20°F)
SF-71MC	100% CO ₂	510 (74,000)	550 (80,000)	28.0	95(70)	75(55)
	Ar-20% CO ₂	540 (78,000)	605 (88,000)	28.0	110(81)	90(66)
AWS A5.20 E71T1-12C,-12M		≥ 390 (56,000)	490~620 (70,000~ 90,000)	≥ 22	≥ 27J at -29°C (≥ 20ft · lbs at -20°F)	

❖ Chemical Analysis of all weld metal(wt%)

Consumable	Shielding gas	C	Si	Mn	P	S
SF-71MC	100% CO ₂	0.040	0.40	1.20	0.010	0.012
	Ar-25% CO ₂	0.040	0.50	1.41	0.010	0.014
AWS A5.20 E71T1-12C,-12M		≤ 0.12	≤ 0.9	≤ 1.60	≤ 0.03	≤ 0.03


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

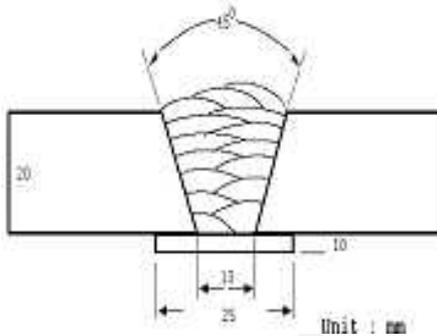

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.6mm (1/16in)
Shielding Gas	: 100% CO ₂ Ar-20%CO ₂
Flow Rate	: 20 ℓ /min
Amp./ Volt.	: 320A / 32V (100% CO ₂) 320A / 30V (Ar-20%CO ₂)
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T (°C, °F)
Interpass Temp	: 150±15°C (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Shielding gas	Tensile Test			CVN Impact Test J(ft · lbs)	
		YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18°C (0°F)	-29°C (-20°F)
SF-71MC	100% CO ₂	500 (73,000)	540 (78,000)	28.5	90(66)	70(52)
	Ar-20% CO ₂	545 (79,000)	600 (87,000)	28.5	100(74)	85(63)
AWS A5.20 E71T1-12C,-12M		≥ 390 (56,000)	490~620 (70,000~ 90,000)	≥ 22	≥ 27J at -29°C (≥ 20ft · lbs at -20°F)	

❖ Chemical Analysis of all weld metal(wt%)

Consumable	Shielding gas	C	Si	Mn	P	S
SF-71MC	100% CO ₂	0.040	0.41	1.23	0.011	0.012
	Ar-25% CO ₂	0.040	0.55	1.42	0.010	0.012
AWS A5.20 E71T1-12C,-12M		≤ 0.12	≤ 0.9	≤ 1.60	≤ 0.03	≤ 0.03

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Welding Efficiency

❖ Deposition Rate & Efficiency

Consumable (size)	Shielding Gas	Welding Conditions		Wire Feed Speed m/min (in/min)	Deposition Efficiency(%)	Deposition Rate kg/hr(lb/hr)
		Amp. (A)	Volt. (V)			
1.2mm (0.045 in)	100%CO ₂	280	32	12.7(500)	86~88	4.8(11)
	Ar-20%CO ₂	280	30	12.7(500)	87~89	5.0(11)
1.6mm (1/16 in)	100%CO ₂	330	32	8.3(325)	86~88	5.3(12)
	Ar-20%CO ₂	330	30	8.3(325)	87~89	5.5(12)
Remark					Deposition efficiency =(Deposited metal weight/Wire weight used)×100	Deposition rate =(Deposited metal weight/Welding time,min.)×60

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Diffusible Hydrogen Content

❖ Welding Conditions

Diameter	: 1.6mm (1/16 in)	Amps / Volts	: 260A / 28V
Shielding Gas	: 100%CO ₂ , Ar-20%CO ₂	Stick-Out	: 20~25mm (0.79~0.98in)
Flow Rate	: 20 l/min	Welding Speed	: 30 cm/min (12 in/min)
Welding Position	: 1G (PA)	Current Type & Polarity	: DC(+)

❖ Hydrogen Analysis Using Gas Chromatography Method

Hydrogen Evolution Time	: 72 hrs
Evolution Temp.	: 45 °C (113°F)
Barometric Pressure	: 780 mm-Hg

❖ Result(ml/100g Weld Metal)

X1	X2	X3	X4
6.8	6.9	6.5	6.8

Average Hydrogen Content 6.8 ml / 100g Weld Metal



Proper Welding Condition

❖ Proper Current Range

Consumable	Shielding Gas	Welding Position	Wire Dia.	
			1.2mm (0.045 in)	1.6mm (1/16 in)
SF-71MC	100%CO ₂ or Ar-20~25%CO ₂	F	100~280Amp	150~360Amp
		HF	100~280Amp	150~360Amp
		V-Up & OH	140~260Amp	180~300Amp
		V-Down	100~280Amp	150~360Amp

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Approvals

❖ Shipping Approvals

Welding Position	Shielding gas	Register of shipping & Size	
		ABS	LR
All V-Down	100%CO ₂	3YSA H10 1.2~1.6mm (0.045~1/16in)	3YS H10 1.2~1.6mm (0.045~1/16in)
All V-Down	Ar-25%CO ₂	3YSA H10 1.2~1.6mm (0.045~1/16in)	3YS H10 1.2~1.6mm (0.045~1/16in)

❖ F No & A No

F No	A No
6	1

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.